

® = registered Trademark of BASF SE

Irgafos[®] 168

Hydrolytically stable phosphite processing stabilizer

Characterization

Irgafos 168 is a hydrolytically stable phosphite processing stabilizer. As a secondary antioxidant, Irgafos 168 reacts during processing with hydroperoxides formed by autoxidation of polymers preventing process induced degradation and extending the performance of primary antioxidants.


Chemical name

Tris(2,4-di-tert.-butylphenyl)phosphite

CAS number

31570-04-4

Chemical formula

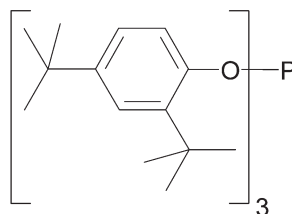

Molecular weight

646.9 g/mol

Applications

The application range of Irgafos 168 – synergistically combined with other BASF anti-oxidants – comprises polyolefins and olefin-copolymers such as polyethylene (e. g. HDPE, LLDPE), polypropylene, polybutene and ethylene-vinylacetate copolymers as well as polycarbonates and polyamides. The blends can also be used in polyesters, styrene homo- and copolymers, adhesives and natural and synthetic tackifier resins, elastomers such as BR, SEBS, SBS, and other organic substrates. Irgafos 168 blends can be used in combination with light stabilizers of the Uvinul[®], Tinuvin[®] and Chimassorb[®] range.

Features/benefits

Irgafos 168 is an organophosphite of low volatility and is particularly resistant to hydrolysis. It protects polymers which are prone to oxidation, during the processing steps (compounding/pelletizing, fabrication and recycling) from molecular weight change (by chain scission or crosslinking) and prevents discoloration.

Irgafos 168 performs best when combined with other BASF antioxidants. Blends of Irgafos 168 with hindered phenols of the Irganox[®] range (Irganox B-blends) are particularly effective. The hindered phenols additionally provide storage stability and give the polymer long term protection against thermooxidative degradation. Irgafos 168 comprised in phenol free systems with other appropriate BASF stabilizers addresses specific stabilization requirements.

Product forms	Irgafos 168	white, free-flowing powder
	Irgafos 168 FF	white, free-flowing granules
Physical properties	Melting range	183–186 °C
	Specific gravity (20 °C)	1.03 g/ml
	Bulk density	
	Powder	480–570 g/l
	FF	480–550 g/l
	Solubility (20 °C)	g/100 g solution
	Acetone	1
	Chloroform	36
	Cyclohexane	16
	Ethanol	0.1
	Ethyl acetate	4
	n-Hexane	11
	Methanol	<0.01
	Dichloromethane	36
	Toluene	30
	Water	<0.01

Health & Safety

Irgafos 168 exhibits a very low order of oral toxicity and does not present any abnormal problems in its handling or general use.

Detailed information on handling and any precautions to be observed in the use of the product(s) described in this leaflet can be found in our relevant health and safety information sheet.

Note

The descriptions, designs, data and information contained herein are presented in good faith, and are based on BASF's current knowledge and experience. They are provided for guidance only, and do not constitute the agreed contractual quality of the product or a part of BASF's terms and conditions of sale. Because many factors may affect processing or application/use of the product, BASF recommends that the reader carry out its own investigations and tests to determine the suitability of a product for its particular purpose prior to use. It is the responsibility of the recipient of product to ensure that any proprietary rights and existing laws and legislation are observed. No warranties of any kind, either expressed or implied, including, but not limited to, warranties of merchantability or fitness for a particular purpose, are made regarding products described or designs, data or information set forth herein, or that the products, descriptions, designs, data or information may be used without infringing the intellectual property rights of others. Any descriptions, designs, data and information given in this publication may change without prior information. The descriptions, designs, data and information furnished by BASF hereunder are given gratis and BASF assumes no obligation or liability for the descriptions, designs, data or information given or results obtained, all such being given and accepted at the reader's risk.

September 2010